

AD 642332

NRL Report 6424

Kinetics of Excess Solute Precipitation in Liquid Sodium Solutions

T. A. KOVACINA, P. G. JOHNSON, AND R. R. MILLER

*Inorganic and Nuclear Chemistry Branch
Chemistry Division*

September 1, 1966

CLEARINGHOUSE FOR FEDERAL SCIENTIFIC AND TECHNICAL INFORMATION		
Hardcopy	Microfiche	
\$3.00	\$.65	15 pp/ps
1 ARCHIVE COPY		



DDC
RECEIVED
NOV 28 1966
C

NAVAL RESEARCH LABORATORY
Washington, D.C.

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

Kinetics of Excess Solute Precipitation in Liquid Sodium Solutions

T. A. KOVACINA, P. G. JOHNSON, AND R. R. MILLER

*Inorganic and Nuclear Chemistry Branch
Chemistry Division*

Abstract: The precipitation characteristics of excess silver and calcium solutes in their respective liquid sodium solutions were studied in the temperature range of 425 to 150°C and the concentration range of approximately 20.0 to 0.10 weight-percent of solute. The excess solute was observed to precipitate out of the bulk of the respective solution as rapidly as the temperature was reduced. The data obtained best fit the empirical equation

$$\frac{C_0 - C_T}{C_0} = \frac{(\Delta T \times \Delta t)K}{d^2},$$

where C_0 is the initial solute saturation (number of atoms per gram of sodium) and C_T is the concentration at any subsequent lower temperature. The quantity $(C_0 - C_T)/C_0$ is then the fraction of the total solute that precipitated out of solution; this excess was observed to be directly proportional to the product of the temperature decrement ΔT (°C) and corresponding elapsed cooling time Δt (min) and inversely proportional to the square of the interatomic solute distance d (cm). The factor K is a proportionality factor assumed to be nearly constant over the concentration and temperature range of the solutions investigated.

INTRODUCTION

This investigation was undertaken as part of a broad program to measure the properties of liquid metals. The main objective of this investigation was to establish any time lag for excess solute precipitation when an initially saturated liquid sodium solution is continuously cooled at a known rate under stirred conditions. Such time-lag information is of value for the prediction of mass transfer and corrosion rates of structural material components in dynamic liquid metal systems. Although silver and calcium have high solubilities in liquid sodium and would not be considered for practical use in heat transfer systems, silver-sodium and calcium-sodium binary systems were expediently chosen for this investigation for the following reasons:

1. Established phase diagrams of both systems indicated only liquidus regions existed over comparable temperature but different solubility ranges. On cooling in these liquidus regions, no solid compound formed; the only solid phase was excess solute material.

2. The solubility of silver at 425°C is approximately 20 weight-percent, while that of calcium at the same temperature is less than 3 weight-percent. The difference in solubilities between the two systems studied afforded an opportunity to investigate the dependence of solute concentration on the precipitation characteristics in addition to the differential solute species effect.

3. Precise and conventional analytical procedures for the determination of both silver and calcium in sodium metal were readily available over the concentration ranges to be encountered.

4. A relationship could be derived between the excess solute precipitation rate parameters of such concentrated solutions that might be reasonably extrapolated to dilute solutions of materials more practical for heat transfer systems, since the dilute solutions lack analytical precision and phase diagram certainties.

APPARATUS AND SAMPLING SYSTEM

The solubility apparatus is diagrammed in Fig. 1. With the exception of the auxiliary glass sampling and inert gas/vacuum port attached to the top of the apparatus through a Kovar metal-to-glass seal, the solubility container was made

NRL Problem C:06-01; Project RR-001-05-41-4850. This is a final report on this phase; work is continuing on the general problem. Manuscript submitted April 21, 1966.

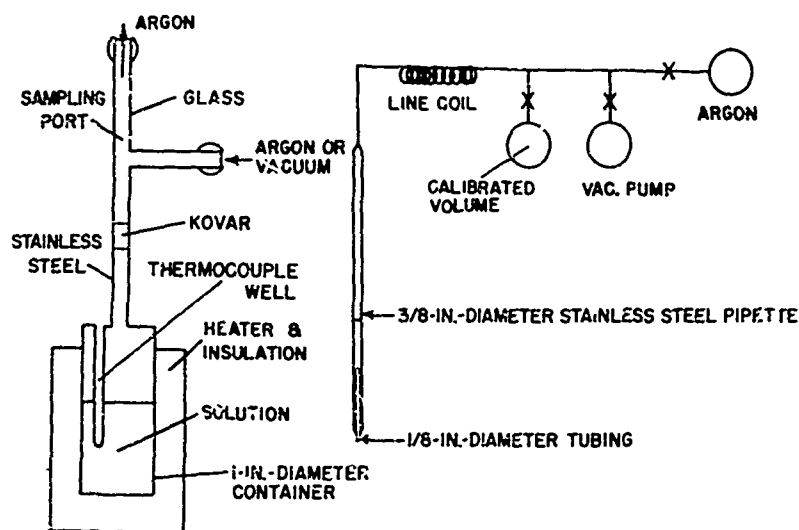


Fig. 1 — Solubility apparatus and sampler. A bucket-dip sampler was also used but gave indeterminate results. The solution was sampled through the sampling port also used to exit the argon atmosphere.

of type 347 stainless steel, known to have good corrosion resistance to liquid sodium. The solubilities of stainless steel components in liquid sodium have been established (1) to be in the low parts per million region over the temperature range of this study. The container was assumed to be inert to the liquid sodium in view of the high solubility systems that were studied.

The liquid sodium solutions were sampled using two different techniques. The bucket-dip technique gave mainly a sample of the solution surface, while the gas-flow-pipette technique gave a bulk liquid sample. The results of both sampling techniques were compared and evaluated in the perspective of the objective of this investigation. Both the buckets and pipettes were made of type 347 stainless steel also. The pipette, 3/8 inch in diameter and 12 inches long with a 4-1/2-inch length of 1/8-inch-diameter tubing concentrically welded in place at the tip, is shown in Fig. 1 also. This pipette design was used as a precaution against loss of sample. Sampling with tubing simply constricted at the tip proved unreliable, as the siphoning action necessary to withdraw a 2 to 4 gram sample of solution required only a slightly reduced pressure from atmospheric.

The reaction vessel was heated by a Nichrome heating element. The solution was stirred electromagnetically during the initial temperature equilibrium period, but the stirrer was turned off during the subsequent cooling period. The tem-

perature of the system was determined within $\pm 2^\circ\text{C}$ by a chromel-alumel thermocouple contained in a well and was automatically recorded on a strip chart of a controlling potentiometer.

PROCEDURE

Approximately 50 grams of sodium were vacuum distilled from a nickel still into a Pyrex receiver fitted with a sintered glass filter frit. The sodium was heated to just above the melting point and filtered by differential argon pressures into the apparatus that contained the required quantity of solute material necessary to saturate the volume of liquid sodium at the highest temperature of the cooling range. The purity of the silver was 99.999 weight-percent. The calcium was electrolytic grade of nominal 99 weight-percent purity.

The solubility apparatus was sealed off from the filter and the internal pressure adjusted with purified argon such that the system was at atmospheric pressure at the sampling temperature. The apparatus was transferred to the controlled furnace assembly and gradually heated to the maximum temperature of the run. The liquid sodium was allowed to equilibrate with the metallic solute material for at least 48 hours under stirred conditions. The solution was then checked for initial solute concentration by both sampling techniques. All sampling was against a backflow of purified

argon with the electromagnetic stirrer off. The argon flow was introduced to the apparatus through the side arm connected to the auxiliary vacuum/inert gas system and exited into the room atmosphere through the vertical sampling port.

After the power to the furnace was turned off, the solution was allowed to cool by ambient room air conditions. Almost-simultaneous sampling by both techniques was done at various points along the cooling range. To avoid atmospheric contamination of the solution the pipettes were highly evacuated and purged with purified argon before insertion in the sampling port, and the buckets were simply purged with a fine jet of purified argon. Both the buckets and pipettes were allowed to remain just above the solution surface for variable time periods of at least 3 minutes before dipping, depending on the sampling frequency, for preheating to as near temperature equilibrium with the solution as possible. During sampling, the pipette was inserted to a predetermined solution depth with purified argon flowing out the tip. The argon flow was then stopped and the gas volume of the auxiliary pipette sampling system cracked into a partially evacuated calibrated volume such that a 2 to 4 gram sample of solution was siphoned from the predetermined depth. The pipette was then removed from the bulk solution and allowed to cool in the upper region of the glass sampling port. The pipette, containing the sample, was then removed from the apparatus, and the sampling sequence was repeated at a different temperature with a new pipette. The above-described sampling procedure maintained a bright shiny surface on the solution after continual sampling of at least 3 hours as evidenced by the visual appearance of the bucket samples; the bright shiny surface indicated minimal atmospheric contamination of the liquid.

The solute concentrations of the nonequilibrium temperature samples were compared with known equilibrium solubility values at the same temperature, and differences in concentration were the criteria used for investigation of supersaturated or colloidal solutions. The excess solute precipitation rate was determined by comparison of the solute concentrations of the nonequilibrium temperature samples with the initial solute concentration of the liquid sodium at zero time.

The stability of general solution conditions and/or the excess solute precipitation rate are important considerations that require qualification in ΔT liquid sodium systems and were the phenomena of principal interest under investigation in this study.

RESULTS

Samples, removed by the bucket technique, of a continuously cooled (425 to 157°C) sodium solution of silver were dissolved and analyzed for sodium content by simple acid-base titration and for silver content by the chloride gravimetric method. These preliminary results are plotted in Fig. 2. The curves produced were typically S-shaped and indicated apparent colloidal suspensions and/or supersaturated solution conditions over most of the cooling range when compared to the equilibrium solubility curve fitted to the observed solution cooling rate data.

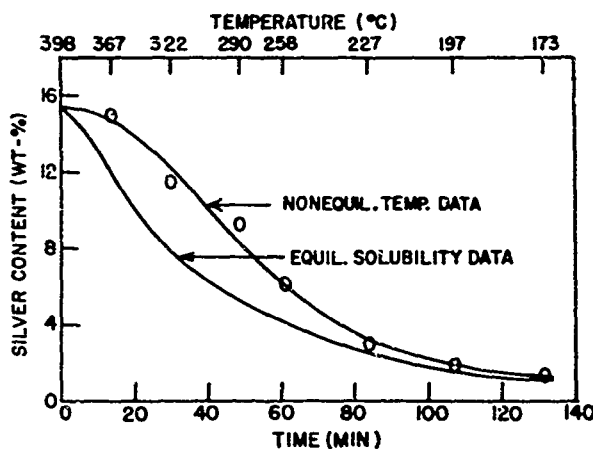


Fig. 2 — The apparent colloidal suspension of silver in liquid sodium as determined from bucket-dip samples

Samples, removed by the same bucket technique, of a continuously cooled (425 to 158°C) sodium solution of calcium were analyzed for calcium volumetrically by an EDTA titration method (2). The results are plotted in Fig. 3 in the same manner as described for the silver-sodium solution. The curve produced is likewise S-shaped—however with a much greater degree of apparent supersaturation and/or colloidal suspension evident than in the former case, especially over the initial part of the cooling

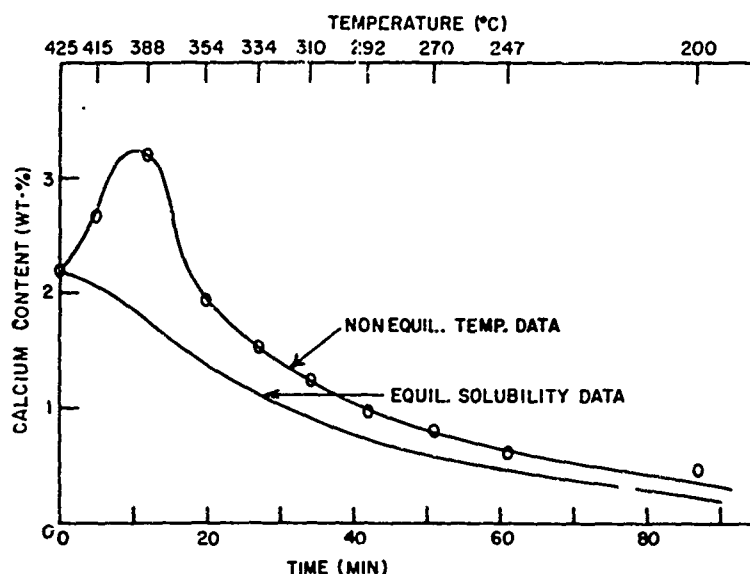


Fig. 3 — The apparent colloidal suspension of calcium in liquid sodium as determined from bucket-dip samples

curve. The high peak region of the curve was reproducible and was further investigated in light of both surface-active phenomena and localized thermal effects of the cooled solution. The surface tension values of calcium and sodium are reported (3,4) to be relatively close. Contaminants such as oxygen in the solution, combined as CaO (CaO is thermodynamically more stable than Na_2O), would tend to lower (5) the surface tension of the calcium.

When the solute has a lower surface tension than the solvent, excess solute is deposited in a film at the surface as the temperature of the solution is decreased. It was reasonable to assume that conditional requirements for surface-active phenomena were closely approximated. Localized thermal effects, especially in the solution surface as cooling occurred, due to the geometry of the experimental setup were also believed to have contributed to the observed anomaly. In order to circumvent any deleterious surface effects inherent in the sampling technique used, two procedural changes were made. The method of sampling the solution was changed primarily to more accurately reflect the precipitation behavior of the true solute specie in the bulk of the liquid. The new method (which was shown in Fig. 1) was a gas-bubbling-pipette technique which broke up the surface film and enabled a bulk sample of the solution to be taken. The second change entailed sample removal from near the

thermocouple well tip, which gave a more accurate sampling temperature and also obviated any localized thermal effects in the surface of the cooled solution.

The experiments were repeated on both the silver and calcium solutions, incorporating the above-described changes. Although the silver-sodium solution was not concerned with surface-active phenomena due to the relatively high surface tension of silver, the localized thermal effects phenomena, however, required qualification. In the interest of further reproduction of the preliminary data, the bucket sampling technique was also employed, almost simultaneously with the gas-flow-pipette technique, during cooling of the respective solutions.

In Fig. 4 are shown the usual comparative plots of solute concentration versus temperature, in terms of elapsed cooling time, with equilibrium solubility values at corresponding temperatures for the silver solution using both sampling techniques. The bucket-sampled data reproduced the preliminary results, while the pipette data correspond with equilibrium solubility values, which indicated that the excess solute precipitated and settled out of the bulk solution as rapidly as the temperature was reduced.

The results of the calcium-sodium nonequilibrium temperature experiment compared with equilibrium solubility values at corresponding temperatures using both sampling techniques

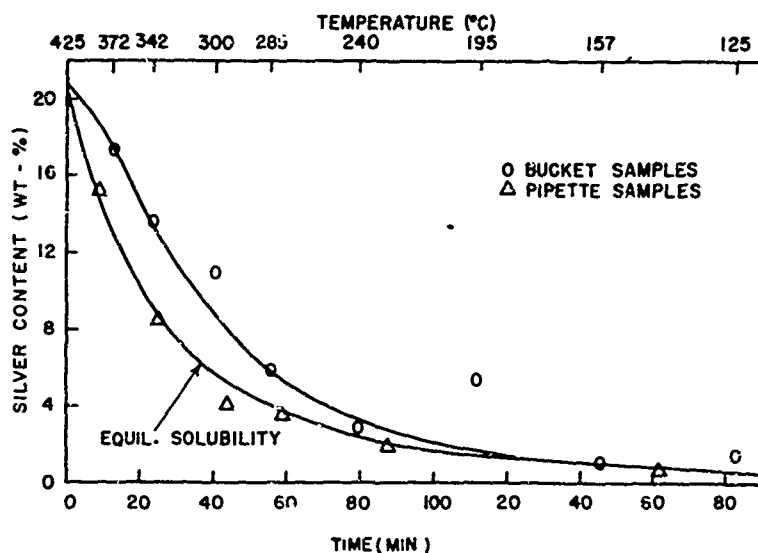


Fig. 4 — Comparison of the apparent colloidal suspension of silver in liquid sodium as determined from bucket-dip samples with equilibrium solubility values as reflected by pipette samples

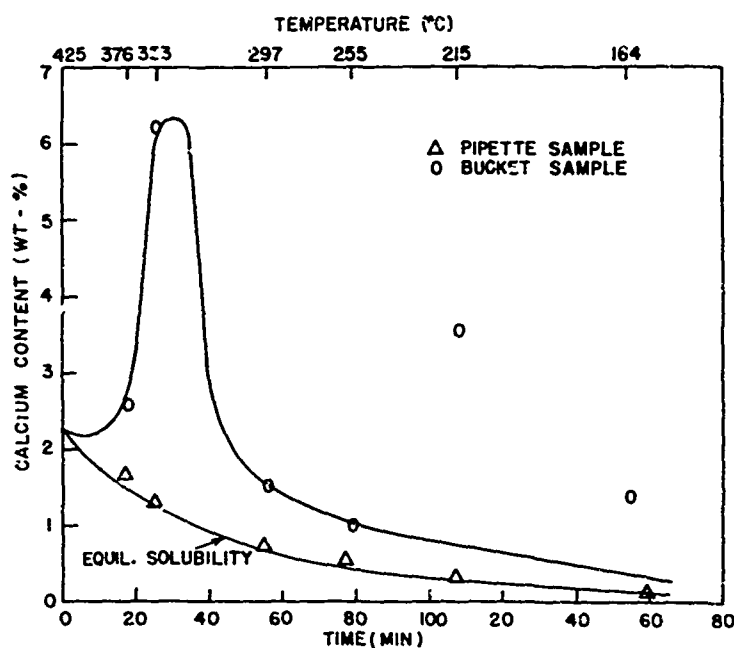


Fig. 5 — Comparison of the apparent colloidal suspension of calcium in liquid sodium as determined from bucket-dip samples with equilibrium solubility values as reflected by pipette samples

are shown in Fig. 5. The same general conclusions were drawn as in the case of the silver-sodium repeat experiment. The results of the pipette samples likewise indicated no measurable time lag for excess solute precipitation at the solution cooling rate and solute concentration levels encountered.

DISCUSSION

As the exact nature of the surface effects phenomena uncovered by the bucket sampling technique was indeterminate, the further treatment of the results, in the perspective of the aforementioned objective of this study, will reflect

only the pipette-sampled data, which were considered to be most characteristic of the bulk of the solution. In order to correlate the most significant system parameters concerned with the excess solute precipitation rate of a liquid sodium solution, a simple skeletal model of the solute matrix was constructed. A cubic lattice geometrical cell configuration was assumed, one side of which is shown in Fig. 6. The interatomic solute spacing d was calculated at a particular temperature from solubility data. From a knowledge of the solute concentration per unit cube of solution, the number of solute atoms on a side of unit length was readily calculated, and assuming a homogeneous distribution of solute atoms in the liquid the distance between the solute atoms was determined.

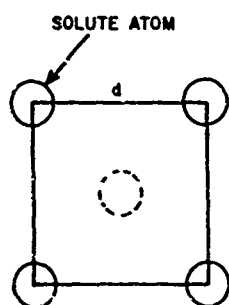


Fig. 6 - Skeletal model of the solute matrix. The dashed atom is in an adjacent plane.

The broken circle in the model diagram designates an excess solute atom lying in an adjacent plane. When the temperature of the solution is decreased, the excess solute atoms are no longer bound to the sodium but become mutually attractive instead. A physical attraction or collision between the excess solute atoms is necessary for precipitation to occur. From a purely statistical point of view, the probability that a collision will occur between two excess solute atoms lying in parallel planes can be expressed as approximately equal to the ratio of the cross sectional area of a solute atom to the planar area d^2 . Thus the precipitation rate is expected to vary inversely as the square of the interatomic distance ($1/d^2$).

If C_0 is the number of solute atoms per gram of sodium at a given saturation temperature, and C_T is the number at any subsequent temperature which is lower by an amount ΔT , then the quantity $(C_0 - C_T)/C_0$ connotes the excess solute fraction available for precipitation as the solution is cooled. The precipitation rate, namely, the excess fraction

that precipitates out of solution per increment of cooling and per increment of time, is then

$$\frac{C_0 - C_T}{C_0} \times \frac{1}{\Delta T \times \Delta t},$$

where Δt is the elapsed cooling time (minutes) corresponding to ΔT ($^{\circ}\text{C}$). If the precipitation rate is inversely proportional to d^2 , the final empirical equation is

$$\frac{C_0 - C_T}{C_0} \times \frac{1}{\Delta T \times \Delta t} = \frac{K}{d^2},$$

where K is a factor characteristic of the liquid sodium solution including expressions for the nucleation and growth of crystallites from cooled melts. A fit of the observed data of the continuously cooled sodium solutions of both calcium and silver to the above equation is shown in Fig. 7. For both solutions studied, the same fairly smooth curve can be drawn through the points. It is interesting to note that only the second power of the d term in the equation was successful in normalizing the precipitation rate data of both solutions.

If the extension of the empirical equation developed is made to include highly dilute solutions such as would be experienced in practical liquid sodium heat transfer systems, the d^2 term would be much larger. As the dilute solution is cooled, the Δt term of the equation will have to be commensurately greater for the equation to apply, which would indicate that long periods of time would be required for the excess solute to precipitate out completely. The prospect of supersaturated conditions in continuously cooled dilute sodium solutions is not unreasonable in view of extrapolation of the measured parameters of the concentrated solutions studied.

The nature of the precipitation process of the excess solute is expected to be a monomolecular reaction. The solute atoms are bound to the solvent atoms in a finite ratio at a particular temperature consistent with solubility considerations. As the temperature of the solution is continuously decreased, a smaller solute-to-solvent atom ratio results. This process is continuous until at the freezing point of the solution, the total quantity of solute atoms initially present is excessive. The precipitation process is considered to be analogous to the decomposition of a compound into another compound of a degraded

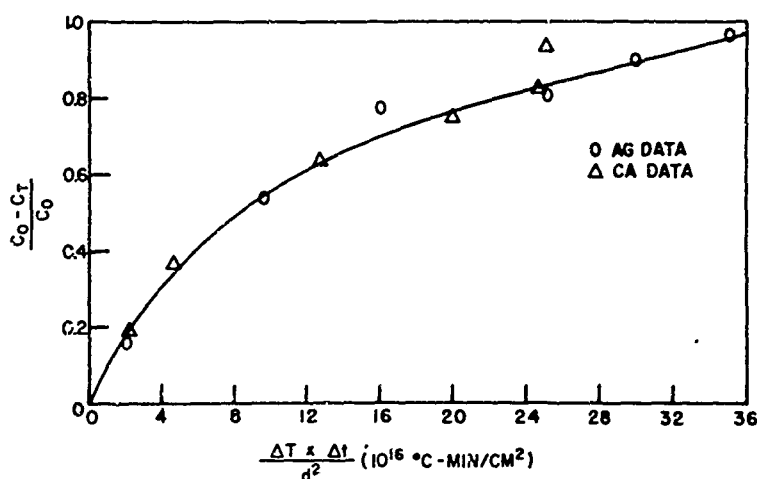


Fig. 7 - Effect of the interatomic solute distance on the precipitation of excess solute in liquid sodium

solute-to-solvent atom ratio and excess solute as the solution is cooled to a lower temperature.

Monomolecular reactions are known to follow the exponential rate law $N/N_0 = e^{-kt}$ and can be derived for the excess solute precipitation process. The rate of change of specific number of solute atoms as the solution is cooled to a lower temperature is set proportional to the number of solute atoms initially present:

$$-\frac{dN}{dt} = kN, \quad (1)$$

which can be expressed as

$$\int \frac{dN}{N} = -k \int dt \quad (2)$$

or

$$\ln N = -kt + a. \quad (3)$$

The integration constant a is evaluated from the limit $N = N_0$ when $t = 0$, which gives $a = \ln N_0$. Thus Eq. (3) becomes

$$\ln \frac{N}{N_0} = -kt \quad (4)$$

or

$$N = N_0 e^{-kt}. \quad (5)$$

The constant k is then the precipitation rate constant for the excess solute specie. If the logarithm of the specific number of solute atoms in solution is plotted versus the elapsed cooling time, and if the reaction rate is first order, the numerical value of k can be determined from

the slope of the resulting straight line. Such plots of the data observed for the continuously cooled sodium solutions of both calcium and silver are shown in Fig. 8. The calcium data fit the exponential rate law quite well over the entire temperature range studied. The calculated slope of the straight line produced gave a value of 0.0173 reciprocal minutes for k . However, the fit of the silver data did not appear to apply over the entire temperature range but only after an initial transient temperature range of 425 to 350°C, after which the slope of the line corresponded to that observed for the calcium data.

Two different rate constants are clearly discernible in the log-Ag-concentration-versus-time plot. The composite curve was resolved into its component parts by back extrapolation of the tail portion to zero time and subtraction of the extrapolated straight line from the original curve. The k value for the initial transient component was calculated to be 0.0577 reciprocal minutes or a factor of 3.3 times greater than that of the second component. The phenomena ascribed to the dual precipitation rate behavior of excess silver solute are not readily determinable.

SUMMARY

Initially saturated sodium solutions of both silver and calcium were continuously cooled and continually examined for general conditions of supersaturation and/or colloidal suspension. Continual sampling of the bulk of the solutions

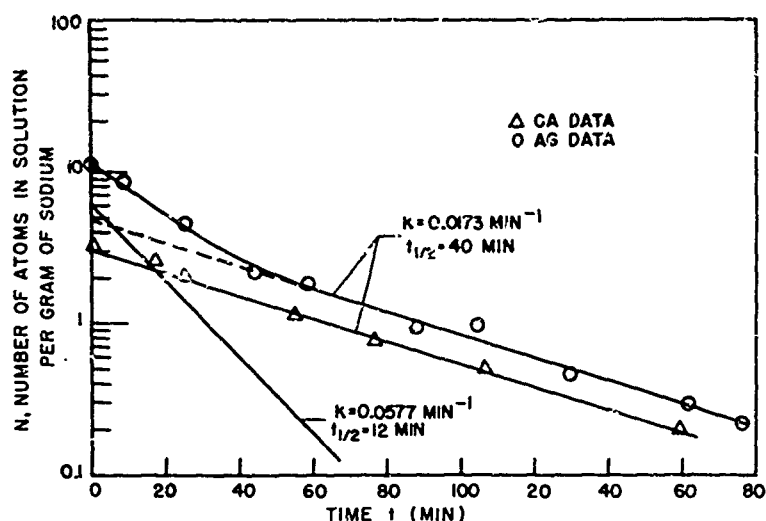


Fig. 8 — Exponential decay of the number of solute atoms remaining during excess solute precipitation in liquid sodium solutions. The precipitation rate constant k is determined by applying Eq. (4) to the linear plots. The curve giving $k = 0.0577 \text{ min}^{-1}$ is the difference between the curve for silver and the dashed extrapolation of its linear portion.

and analysis for the respective solute species did not indicate a measurable time lag for excess solute to be removed from the liquid. The precipitation of the excess calcium solute was observed to follow the exponential rate law over the entire cooling range studied. The precipitation of the excess silver solute showed a deviation from the exponential rate law, and two different rate constants were indicated. The excess fraction of total solute of either specie studied that precipitated out of solution at any point along the cooling curve was observed to be a direct function of the temperature decrement and elapsed time and an inverse function of the square of the calculated interatomic solute distance. Extrapolation of the above-mentioned parameters to more dilute continuously cooled sodium solutions tend to indicate that the equivalent of supersaturated and/or colloidal conditions are possible. This would be a

desirable effect in a dynamic system such as a practical heat transfer system. The excess solute entrained in the liquid sodium stream would be returned to the heat source and redissolved, in lieu of continuous corrosion of container or structural materials in the hot zone and precipitation with subsequent settling in the cold zone of the loop.

REFERENCES

1. Baus, R.A., Bogard, A.D., Grand, J.A., Lockhart, L.B., Jr., Miller, R.R., and Williams, D.D., Proc. 1st. Intern. Conf. Peaceful Uses Atomic Energy, Geneva, 1955, New York: United Nations, 1956, vol. 9, pp. 356-363
2. Padhye, V.P., Analyst **82**:634-8 (1957)
3. Addison, C.C., Coldrey, J.M., and Pulham, R.J., *J. Chem. Soc.* 1963, 1227-1231
4. Addison, C.C., Kerridge, D.H., and Lewis, J., *J. Chem. Soc.* 1954, 2861-2866
5. Bondi, A., *Chem. Rev.* **52**:417 (1953)

Security Classification

DOCUMENT CONTROL DATA - R&D		
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)		
1. ORIGINATING ACTIVITY (Corporate author) Naval Research Laboratory Washington, D.C. 20390		2a. REPORT SECURITY CLASSIFICATION Unclassified
		2b. GROUP
3. REPORT TITLE KINETICS OF EXCESS SOLUTE PRECIPITATION IN LIQUID SODIUM SOLUTIONS		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) A final report on one phase of the problem.		
5. AUTHOR(S) (Last name, first name, initial) Kovacina, T. A., Johnson, P. G., and Miller, R. R.		
6. REPORT DATE September 1, 1966	7a. TOTAL NO. OF PAGES 10	7b. NO. OF REFS 5
8a. CONTRACT OR GRANT NO. NRL Problem C06-01	9a. ORIGINATOR'S REPORT NUMBER(S) NRL Report 6424	
b. PROJECT NO. RR 001-05-41-4850		
c.	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
d.		
10. AVAILABILITY/LIMITATION NOTICES Distribution of this document is unlimited.		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY Department of the Navy (Office of Naval Research) Washington, D.C. 20360	
13. ABSTRACT <p>The precipitation characteristics of excess silver and calcium solutes in their respective liquid sodium solutions were studied in the temperature range of 425 to 150°C and the concentration range of approximately 20.0 to 0.10 weight-percent of solute. The excess solute was observed to precipitate out of the bulk of the respective solution as rapidly as the temperature was reduced. The data obtained best fit the empirical equation</p> $\frac{C_0 - C_T}{C_0} = \left(\frac{\Delta T \times \Delta t}{d^2} \right) K$ <p>where C_0 is the initial solute saturation (number of atoms per gr.-m of sodium) and C_T is the concentration at any subsequent lower temperature. The quantity $(C_0 - C_T)/C_0$ is then the fraction of the total solute that precipitated out of solution; this excess was observed to be directly proportional to the product of the temperature decrement ΔT and corresponding elapsed cooling time Δt (min) and inversely proportional to the square of the interatomic solute distance d (cm). The factor K is a proportionality factor assumed to be nearly constant over the concentration and temperature range of the solutions investigated.</p>		

Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Liquid metal coolants						
Liquid metals						
Sodium						
Solvent action						
Structural parts						
Silver						
Calcium						
Solutions						
Chemical precipitation						
Dynamics						

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, roles, and weights is optional.